

Effect of Slag Composition on the Distribution Behavior of Pb between Fe_tO-SiO₂ (-CaO, Al₂O₃) Slag and Molten Copper

Jung-Ho HEO¹⁾, Soo-Sang PARK²⁾ and Joo Hyun PARK^{1),*}

1) School of Materials Science and Engineering, University of Ulsan, Ulsan 680-749, Korea

2) Metals and Materials Research Department, LS-Nikko Copper, Ulsan 70, Korea

Abstract: The distribution behavior of lead between molten copper and Fe_tO-SiO₂ (-CaO, Al₂O₃) slags was investigated at 1473 K and $p(\text{O}_2)=10^{-10}$ atm in view of the reaction mechanism of lead dissolution into the slag. Furthermore, the lead capacity of the slag was estimated from the experimental results. The distribution ratio of lead (L_{Pb}) decreases with increasing amount of CaO (~6wt%) irrespective of Fe/SiO₂ ratio (1.4~1.7). However, the addition of alumina in the slag with Fe/SiO₂=1.5 linearly decreases the L_{Pb} , whereas there is a minimum value at about 4wt%Al₂O₃ at Fe/SiO₂=1.3. The $\log L_{\text{Pb}}$ continuously decreases with increasing Fe/SiO₂ ratio and furthermore, the addition of Al₂O₃ (5~15wt%) into the silica saturated iron silicate slag (Fe/SiO₂ < 1.0) shows the highest Pb distribution ratio. This is mainly due to a decrease in the activity of FeO even at silica saturation condition. The $\log L_{\text{Pb}}$ linearly decreases by increasing the $\log (\text{Fe}^{3+}/\text{Fe}^{2+})$ values. The Pb distribution ratio increases with increasing content of Cu₂O in the slag and the excess free energy of PbO decreases with increasing content of Cu₂O. However, in viewpoint of copper loss into the slag, the silica saturated system containing small amounts of alumina is strongly recommended to stabilize PbO in slag phase at low content of Cu₂O. The 'lead capacity' was defined in the present study and it shows a linear correlation with the activity of FeO in a logarithmic scale, indicating that the concept of lead capacity is a good measure of absorption ability of lead of iron silicate slags and the activity of FeO can be a good basicity index in the iron silicate slag.

Key words: Copper smelting and refining, Lead distribution ratio, Fe_tO-SiO₂ (-CaO, Al₂O₃) slag, Refining, Fe³⁺ to Fe²⁺ ratio, Excess free energy of PbO

1. Introduction

It is very important in copper smelting and refining processes to remove several minor elements such as lead, bismuth, antimony, arsenic and tellurium.^[1,2] Specifically, lead is troublesome impurity which increases the amount of slime in the electro-refining process. Also, from the viewpoint of copper smelting and refining processes, lead is detrimental element that is always present in sulfide concentrates that must be eliminated. Therefore, the content of lead in molten copper should be lowered within appropriate concentration range in a plant operation and thus we need specific knowledge of the effect of slag composition on the thermodynamic behavior of lead in molten slag.

Kim and Sohn examined the effects of CaO, Al₂O₃, and MgO additions on the distribution behavior of lead between an iron silicate slag and liquid copper under a CO-CO₂ atmosphere ($p(\text{O}_2)=10^{-12}\sim 10^{-6}$ atm) at 1523 K and found that the distribution ratio of Pb and the activity coefficient of PbO was not significantly affected by the additives.^[3] The governing factors affecting the Pb solubility in iron silicate slag were proposed as the oxygen potential ($p(\text{O}_2)$) and the ratio of Fe_tO/SiO₂ (or SiO₂ content) in the slag. Matsuzaki *et al.*^[4] calculated the activity coefficient of

PbO (γ_{PbO}) with the regular solution model and plotted the iso- γ_{PbO} contours in the CaO-SiO₂-Al₂O₃ ternary slag at 1623 K. The value of γ_{PbO} decreased as CaO was replaced with SiO₂ at any fixed concentration of Al₂O₃, indicating the basic character of PbO in the slag. The similar tendency of the effect of CaO/SiO₂ ratio on the γ_{PbO} was also reported by Kudo et al.^[5] in the Fe₁O-CaO-SiO₂ system in equilibrium with metallic iron at 1573 K. In this study,^[5] it is interesting that the changes in temperature from 1473 to 1573 K did not have a significant effect on γ_{PbO} in the slag. Degterov and Pelton computed the distribution behavior of lead among matte, slag, and liquid copper at 1523 K and $p(\text{O}_2)=10^{-12}\sim 10^{-5}$ atm under condition from silica saturation to magnetite saturation.^[6] The distribution ratio of Pb decreased with increasing Fe/SiO₂ ratio from silica to magnetite saturation. The small addition of CaO (3wt%) also decreased the Pb distribution ratio. Kashima *et al.*^[7] observed that Pb was distributed among crude copper, white metal, and silica saturated iron silicate slag in rather similar concentrations at 1573 K under controlled SO₂ partial pressure. Also, Acuna and Yazawa found that the lead distribution ratio was in the order of iron silicate > barium ferrite \geq calcium ferrite slag at copper content in matte phase was greater than about 50wt%.^[8]

Even though the effectiveness of slag treatment for the removal of Pb from the Cu melt have been investigated as mentioned above, many of studies focused on the equilibrium distribution behavior of Pb among the Cu/matte/slag system in smelting and converting processes. Therefore, in the present study, the distribution behavior of lead between molten copper and Fe₁O-SiO₂ (-CaO, Al₂O₃) slags was investigated in view of the reaction mechanism of lead dissolution into the slag. Furthermore, the lead capacity of the slag was estimated from the experimental results.

2. Experimental


2.1 Sample preparation

An alloy sample with the composition of Cu-1wt%Pb was preliminarily prepared from pure (99.99% purity) copper and lead. This alloy sample was melted in an alumina crucible (OD; 50 mm, ID; 45 mm, HT; 70 mm) in a highly purified Ar atmosphere using Mg turnings at 773 K for 2 hours at 1473 K. The slag samples divide into two classes that first sample type were prepared by mixing reagent-grade FeO, SiO₂, Al₂O₃, and CaO calcined from CaCO₃ at 1273 K for 10 hours and second sample type were prepared silica-saturated Fe₁O-SiO₂-Al₂O₃ slags under the same condition as mentioned above.

2.2 Measurement

The experiments were carried out using super-kanthal electric furnace with MoSi₂ heating element. A schematic diagram of the experimental apparatus is shown in Figure 1.

The temperature was controlled within ± 2 K using a B-type (Pt-30wt%Rh / Pt-6wt%Rh) thermocouple and a proportional integral differential controller. The equilibration time was predetermined to be 6 hours at 1473 K. The metal (8 g) and slag (5 g) were loaded in a fused magnesia (99.9% purity) crucible (OD; 18 mm, ID; 14 mm, HT; 50 mm). This was placed in an alumina holder (OD; 50 mm, ID; 45 mm, HT; 70 mm) and then hooked with a molybdenum wire. The oxygen partial pressure of the system was controlled by the following reaction,^[9]



[1]

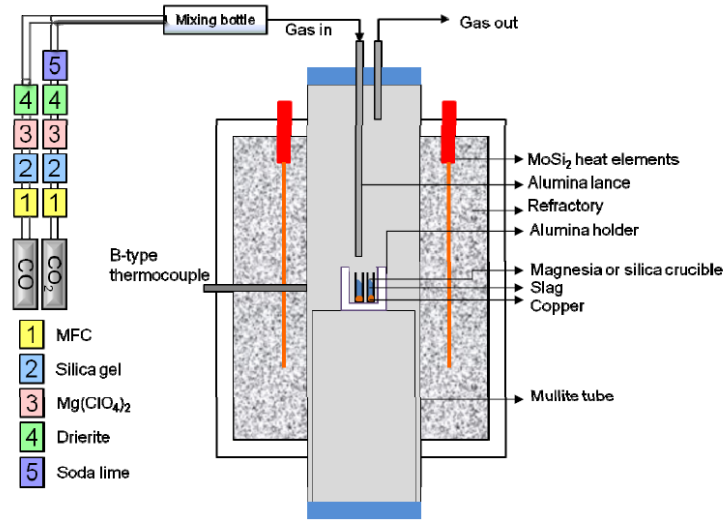


Fig. 1 Schematic diagram of the experimental apparatus.

The gas flow rate was controlled by a mass flow controller. The impurities in the CO_2 and CO gases were removed by passing the gases through the Drierite (W.A. Hammond Drierite Co. Ltd., Xenis, OH), $\text{Mg}(\text{ClO}_4)_2$, silica gel and soda lime.

Under the same experimental conditions as mentioned above, additional experiments were carried out for the equilibration between the silica-saturated $\text{Fe}_t\text{O-SiO}_2\text{-Al}_2\text{O}_3$ slags (5 g) and copper melt (8 g) in a fused quartz crucible (OD; 20 mm, ID; 16 mm, HT; 40 mm) in order to investigate the effect of Al_2O_3 addition on Pb distribution ratio between molten copper and silica saturated slag.

After equilibration was attained, the samples were quickly withdrawn from the hot zone of the furnace and rapidly quenched by flushing Ar gas, followed by dipping it into brine. The slag and metal samples were carefully separated from the crucible, and the metal-slag, metal-crucible and crucible-slag interfaces were removed. The sample was finely ground to powder, and the metal sample was cut into small pieces for chemical analysis. The composition of metal and slag samples was determined using ICP-AES (Optima 5300DV, PerkinElmer). Furthermore, the ferric (Fe^{3+}) to ferrous (Fe^{2+}) ratio in the slags was determined by the titration method using a potassium dichromate.

3. Results and Discussion

3.1 Influence of additives (CaO, Al₂O₃) and Fe/SiO₂ ratio on the distribution ratio of Pb

The distribution ratio of lead (L_{Pb}) between molten copper and Fe₁O-SiO₂ (-CaO, Al₂O₃) slags at 1473 K and $p(O_2)=10^{-10}$ atm is shown in Figure 2 and Figure 3 as a function of the content of CaO and Al₂O₃, respectively, at different Fe/SiO₂ ratio.

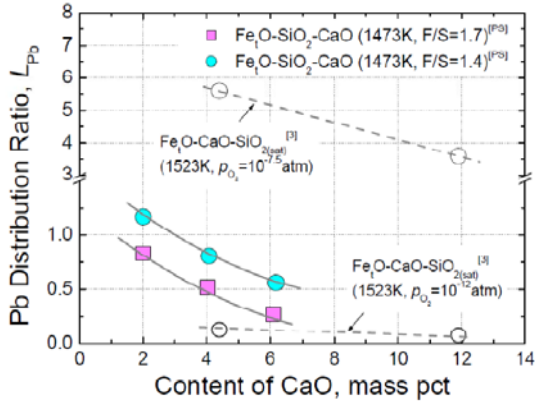


Fig. 2 Influence of CaO on the distribution ratio of lead between molten copper and Fe₁O-SiO₂-CaO slag at 1473 K and $\log p(O_2)=-10$. [PS]; present study.

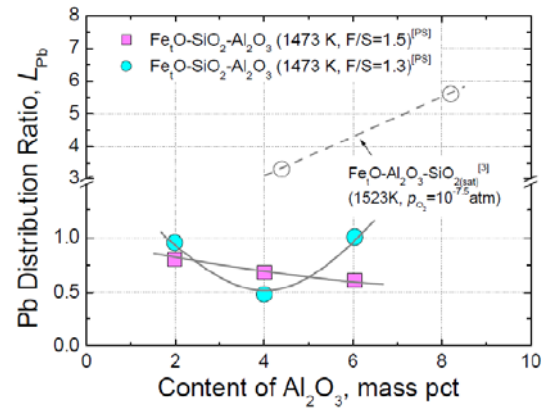


Fig. 3 Influence of Al₂O₃ on the distribution ratio of lead between molten copper and Fe₁O-SiO₂-Al₂O₃ slag at 1473 K and $\log p(O_2)=-10$. [PS]; present study.

The distribution ratio of Pb between metal and slag phase in this study is defined as follows:

$$L_{Pb} = \frac{(\text{wt}\%Pb)}{[\text{wt}\%Pb]} \quad [2]$$

The value of L_{Pb} decreases with increasing amount of CaO irrespective of Fe/SiO₂ ratio. This tendency is qualitatively similar to the results in the literature even at different temperature and oxygen potential,^[3-6] indicating that CaO unambiguously behaves as a basic component (Eq. [4]) in the iron silicate slag based on the following ionic dissolution mechanism.



The addition of alumina in the iron silicate melts with the $Fe/SiO_2=1.5$ linearly decreases the Pb distribution ratio, whereas there is a minimum value at about 4wt% Al_2O_3 at $Fe/SiO_2=1.3$. Therefore, it is suggested that the alumina is considered as a basic component in the former system and in the composition of Al_2O_3 content less than 4wt% in the latter system based on Eq. [5]. However, the alumina behaves as an acidic component in the composition of Al_2O_3 content greater than 4wt% in the latter system based on Eq. [6].^[10]



Actually, the Pb distribution ratio increases with increasing content of alumina in the silica-saturated acidic system from the experimental data measured by Kim and Sohn.^[3] They, however, originally concluded that the addition of Al_2O_3 up to about 8wt% in the silica-saturated slag did not show a significant change in Pb distribution ratio in a logarithmic scale at a given oxygen potential. Reassessment of their experimental data provided the result shown in Figure 3. The amphoteric behavior of alumina in silicate melts (Eqs. [5] and [6]) have been reported in the previous studies.^[10]

The value of L_{Pb} between molten copper and $Fe_tO-SiO_2(-CaO, Al_2O_3)$ slags is shown in Figure 4 as a function of Fe/SiO_2 ratio.

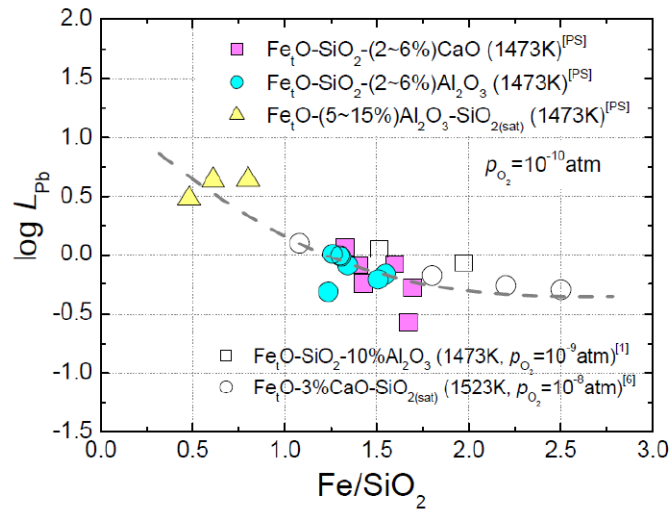


Fig. 4 Influence of Fe/SiO_2 ratio on $\log L_{Pb}$ in the $Fe_tO-SiO_2(-CaO, Al_2O_3)$ slags at 1473 K and $\log p(O_2)=-10$. [PS]; present study.

The $\log L_{Pb}$ continuously decreases with increasing Fe/SiO_2 ratio and this tendency is in good accordance to the literature data.^[1,6] Furthermore, the addition of Al_2O_3 (5~15wt%) into the silica saturated iron silicate slag ($Fe/SiO_2 < 1.0$) shows the highest Pb distribution ratio. This can be understood by taking the variation of the activity of each component into account as follows.

Figure 5 shows the iso-activity contours of each component in the $Fe_tO-SiO_2-Al_2O_3$ slag at 1473 K and $p(O_2)=10^{-10}$

atm, which was calculated using a commercial thermochemical computing package, FactSage™6.2.^[11] This software has been successfully applied in predicting the thermodynamic properties of multi-component metallurgical slags.^[12]

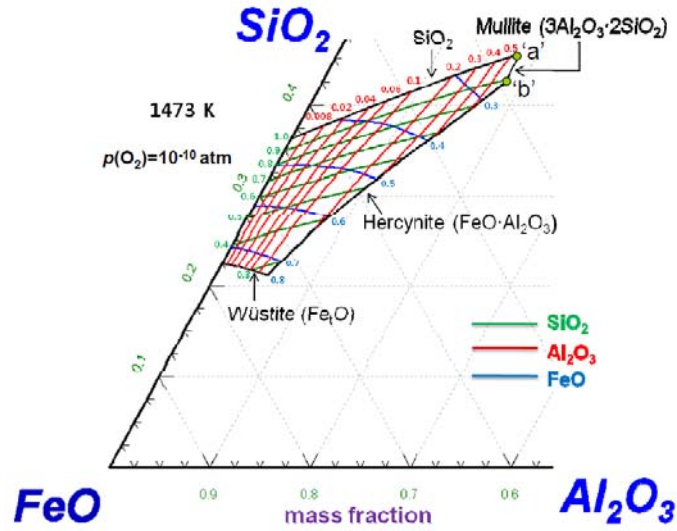


Fig. 5 Iso-activity contours for FeO, SiO₂ and Al₂O₃ in the Fe₁O-SiO₂-Al₂O₃ ternary system at 1473 K and log p(O₂)=-10.

The activity of Al₂O₃ increases up to about 0.6 as the alumina content increases from FeO-SiO₂ side to silica-mullite double saturation point 'a', which is in very good accordance to the following thermodynamic assessment at 1473 K.^[9]



$$a_{\text{Al}_2\text{O}_3} = \left[\frac{K_{[7]} \cdot a_{3\text{Al}_2\text{O}_3 \cdot 2\text{SiO}_2}}{a_{\text{SiO}_2}^2} \right]^{\frac{1}{3}} = K_{[7]}^{1/3} = 0.63 \quad [8]$$

Alternatively, the activity of FeO decreases from about 0.45 to 0.25 with increasing content of alumina at a fixed silica activity, i.e. $a_{\text{SiO}_2} = 1.0$. The activity of FeO at hercynite-mullite double saturation point is in good agreement to the following thermodynamic assessment.^[9]



$$K_{[9]} = \frac{a_{\text{FeO}} \cdot a_{\text{Al}_2\text{O}_3}}{a_{\text{FeO} \cdot \text{Al}_2\text{O}_3}} \quad [10]$$

Combining Eqs. [8] and [10], the activity of FeO at hercynite-mullite double saturation point 'b' ($a_{\text{SiO}_2} = 0.9$) at 1473 K can be given as follows.

$$a_{\text{FeO}} = \frac{K_{[9]}}{K_{[7]}^{1/3}} \times a_{\text{SiO}_2}^2 = 0.27 \quad [11]$$

A decrease in the activity of FeO significantly increases the Pb distribution ratio, which originates from the basic character of FeO in the iron silicate melts, i.e. production of free O^{2-} ions based on Eq. [12].



$$a_{\text{O}^{2-}} = \frac{K_{[12]} \cdot a_{\text{FeO}}}{a_{\text{Fe}^{2+}}} \quad [13]$$


Consequently, a decrease in the activity of FeO, i.e. a decrease in the activity of free O^{2-} ions in the silicate melts assuming the proportionality between them from Eq. [13], the dissolution of Pb into the slag phase was promoted based on the ionic dissolution mechanism given in Eq. [3]. In Figure 5, the activity of FeO is not unity but 0.8 at wüstite saturation line, which is due to the coexistence of Fe_2O_3 , i.e. Fe^{3+} ions under the present conditions. This will be discussed in the following section.

3.2 Influence of $\text{Fe}^{3+}/\text{Fe}^{2+}$ ratio on the distribution ratio of Pb

The ferric-to-ferrous ratio, $\text{Fe}^{3+}/\text{Fe}^{2+}$ in the slag at a fixed temperature is dependent upon slag composition. Larson and Chipman reported that the $\text{Fe}^{3+}/\text{Fe}^{2+}$ ratio increases as CaO content increases at constant oxygen potential in the CaO-FeO- Fe_2O_3 and the CaO-SiO₂-FeO- Fe_2O_3 systems at 1823 K.^[13] Generally, the ferric ion, Fe^{3+} is suggested to be predominant rather than ferrous ion, Fe^{2+} by addition of basic oxide such as CaO, which produces the free O^{2-} ions. Therefore, the equilibrium between Fe^{2+} and Fe^{3+} ions is expressed as follows.^[10]



By combining Eqs. [3] and [14], the $\text{Pb} \leftrightarrow \text{Fe}$ exchange reaction can be deduced as follows.



From the equilibrium constant of Eq. [15], the relationship between $\text{Fe}^{3+}/\text{Fe}^{2+}$ ratio and Pb distribution ratio is deduced as follows.

$$\log L_{\text{Pb}} = -\frac{2}{3} \log \left(\frac{\text{wt}\% \text{Fe}^{3+}}{\text{wt}\% \text{Fe}^{2+}} \right) - \frac{2}{3} \log \left(\frac{f_{\text{Pb}^{2+}}^{1.5} \cdot f_{\text{FeO}_2^-}}{f_{\text{Fe}^{2+}}} \right) + \log f_{\text{Pb}} + \frac{2}{3} \log p_{\text{O}_2} + \log K_{[15]} \quad [16]$$

Thus, $\log L_{\text{Pb}}$ is expected to be inversely proportional to $\log (\text{Fe}^{3+}/\text{Fe}^{2+})$ with the slope of $-2/3$ at a given temperature and oxygen potential assuming that the second activity coefficient term on the right hand side in Eq. [16] would not be significantly affected by slag composition.

Figure 6 shows a relationship between the $\log L_{\text{Pb}}$ and $\log (\text{Fe}^{3+}/\text{Fe}^{2+})$, wherein the linear relationship between them with the slope of about -0.44 is obtained from a linear regression analysis. The slope of the line is slightly lower than the expected value (-0.67) in Eq. [16], which probably originates from the attraction between Pb^{2+} and ferric complex ions with increasing $\text{Fe}^{3+}/\text{Fe}^{2+}$ ratio. This is thermodynamically consistent to the fact that there are several stable lead ferrite compounds such as $\text{Pb}_2\text{Fe}_2\text{O}_5$ (2:1, δ -phase), PbFe_4O_7 (1:2, γ -phase), and $\text{PbFe}_{12}\text{O}_{19}$ (1:6, β -phase).^[14,15]

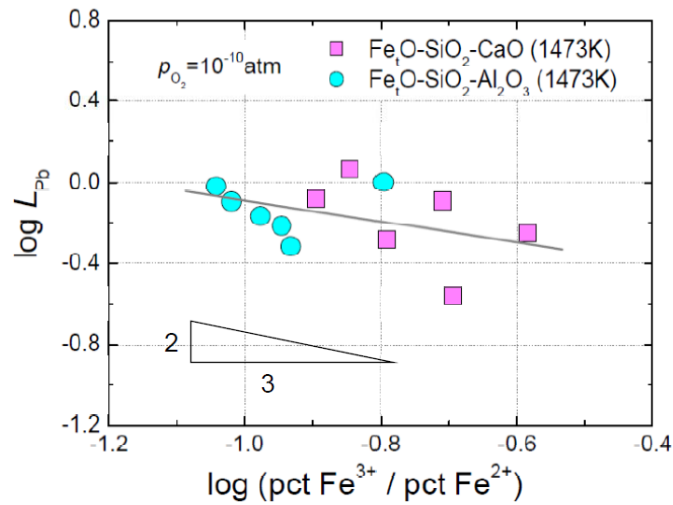


Fig. 6 Relationship between $\log L_{\text{Pb}}$ and $\log (\text{Fe}^{3+}/\text{Fe}^{2+})$ in the $\text{Fe}_1\text{O-SiO}_2$ ($-\text{CaO}$, Al_2O_3) slags at 1473 K and $\log p(\text{O}_2)=-10$.

3.3 Influence of Cu_2O on the distribution ratio of Pb and stability of PbO in slag phase

The effect of Cu_2O on the Pb distribution ratio between molten copper and iron silicate slags at 1473 K is shown in Figure 7.

The Pb distribution ratio increases with increasing content of Cu_2O in the slag. It was known from the previous studies that Pb and Cu are present in the slag as PbO and Cu_2O in molecular form, respectively,^[4,16-19] and thus the

following equilibrium reaction is given at slag/metal interface.

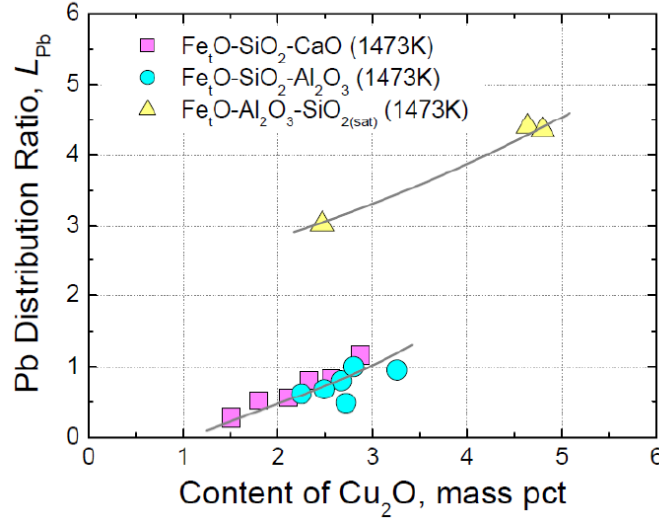



Fig. 7 Influence of Cu_2O content on the distribution of lead between molten copper and $\text{Fe}_1\text{O-SiO}_2$ (-CaO, Al_2O_3) slags at 1473 K and $\log p(\text{O}_2)=-10$.



$$K_{[17]} = \frac{a_{\text{PbO}}}{a_{\text{Pb}} \cdot a_{\text{Cu}_2\text{O}}} = \frac{\gamma_{\text{PbO}} \cdot X_{\text{PbO}}}{\gamma_{\text{Pb}} \cdot X_{\text{Pb}} \cdot \gamma_{\text{Cu}_2\text{O}} \cdot X_{\text{Cu}_2\text{O}}} \quad [18]$$

where $K_{[17]}$, a_i , γ_i and X_i are the equilibrium constant of Eq. [17], the activity, the activity coefficient and the mole fraction of component i , respectively.

On the other hand, the activity coefficient (γ_{PbO}) and thus an excess free energy of PbO ($\Delta G_{\text{PbO}}^{\text{Ex}}$) can be estimated from the following equations.^[9,20]



$$\gamma_{\text{PbO}} = \frac{K_{[19]} \cdot \gamma_{\text{Pb}}^0 \cdot X_{\text{Pb}} \cdot \sqrt{p_{\text{O}_2}}}{X_{\text{PbO}}} \quad [20]$$

$$\Delta G_{\text{PbO}}^{\text{Ex}} = -RT \ln \gamma_{\text{PbO}} \quad [21]$$

where γ_{Pb}^0 is the Henrian activity coefficient of Pb in molten copper, which is known as $\gamma_{\text{Pb}}^0 = 5.27$ at 1473 K.^[20]

The excess free energy of PbO calculated from Eqs. [20] and [21] is plotted against the mole fraction of Cu_2O in Figure 8. The excess free energy of PbO decreases with increasing content of Cu_2O , indicating that Cu_2O is relatively more

acidic than PbO in the copper smelting iron silicate slags. However, in viewpoint of copper loss into the slag, the silica saturated system containing small amounts of alumina is strongly recommended to stabilize PbO in slag phase at low content of Cu_2O .

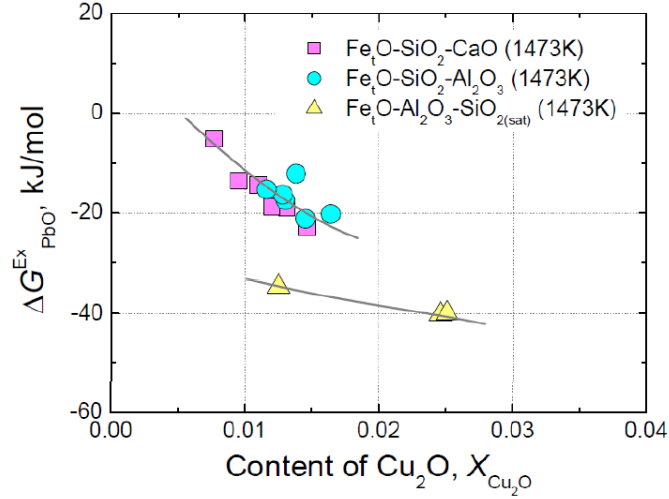


Fig. 8 Excess free energy of PbO in the $\text{Fe}_t\text{O-SiO}_2(-\text{CaO}, \text{Al}_2\text{O}_3)$ slags at 1473 K.

3.4 Correlation between the activity of FeO and the Pb Capacity

From an ionic dissolution mechanism of lead which is given in Eq. [3], the ‘lead capacity’ of the slag can be defined using an equilibrium constant of Eq. [3] as follows.

$$C_{\text{Pb}^{2+}} = \frac{K_{[3]}}{f_{\text{Pb}^{2+}} \cdot a_{\text{O}^{2-}}} = \frac{(\text{wt}\% \text{Pb}^{2+})}{f_{\text{Pb}} \cdot [\text{wt}\% \text{Pb}] \cdot \sqrt{p_{\text{O}_2}}} = \frac{L_{\text{Pb}}}{f_{\text{Pb}} \cdot \sqrt{p_{\text{O}_2}}} \quad [22]$$

Therefore, the lead capacity is a function of the basicity ($a_{\text{O}^{2-}}$) and the stability of Pb^{2+} ion ($f_{\text{Pb}^{2+}}$) at a fixed temperature and it can be calculated from L_{Pb} , p_{O_2} and f_{Pb} in molten copper. The activity coefficient of Pb in molten copper at 1473 K is calculated using Eq. [23], resulting in $f_{\text{Pb}} \sim 1.0$.^[20]

$$\log f_{\text{Pb}} = e_{\text{Pb}}^{\text{Pb}} \cdot [\text{wt}\% \text{Pb}] = -0.0006 \cdot [\text{wt}\% \text{Pb}] \cong 0 \quad [23]$$

By combining Eqs. [13] and [22], the lead capacity can be expressed as a function of FeO activity as follows.

$$\log C_{\text{Pb}^{2+}} = -\log a_{\text{FeO}} + \log a_{\text{Fe}^{2+}} - \log f_{\text{Pb}^{2+}} + \log \frac{K_{[3]}}{K_{[12]}} \quad [24]$$

From Eq. [24], the lead capacity and FeO activity are expected to show a linear relationship with a slope of -1.0 in a logarithmic scale assuming that the composition dependency of $a_{\text{Fe}^{2+}}$ and $f_{\text{Pb}^{2+}}$ is not so critical at a given temperature. In the present study, the activity of FeO in the slag was calculated based on the Regular solution model provided by Banya and Shim.^[21]

Figure 9 shows a relationship between the lead capacity, $\log C_{\text{Pb}^{2+}}$ and the activity of FeO, $\log a_{\text{FeO}}$, wherein a good linearity is observed with the slope of about -1.5 from least square regression method. This is slightly larger than the expected value of -1.0, indicating a change in the $a_{\text{Fe}^{2+}}$ and/or $f_{\text{Pb}^{2+}}$ terms with increasing FeO activity. Hence, it is suggested that an increasing rate of $f_{\text{Pb}^{2+}}$ is relatively larger than that of $a_{\text{Fe}^{2+}}$ by increasing the activity of FeO because of a repulsive force between Fe^{2+} and Pb^{2+} ions. From a linear correlation between lead capacity and FeO activity in Figure 9, the concept of ‘lead capacity’ is a good measure of absorption ability of lead of iron silicate slags and the activity of FeO can be a qualitative basicity index in the slag.

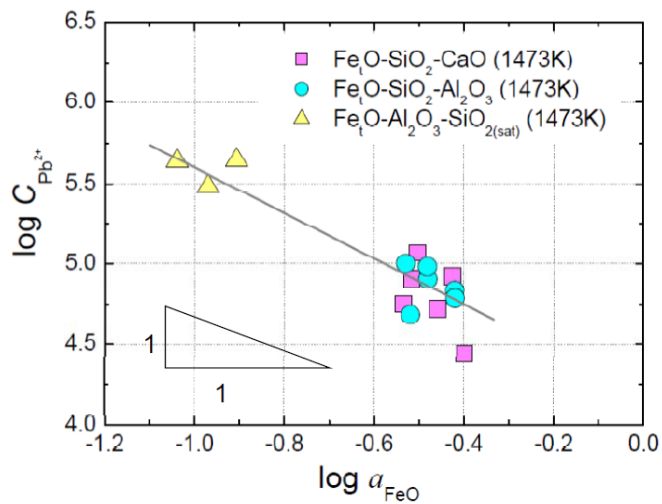


Fig. 9 Correlation between the activity of FeO and the lead capacity in the $\text{Fe}_1\text{O-SiO}_2$ (-CaO, Al_2O_3) slags at 1473 K.

4. Conclusions

- 1) The value of L_{Pb} decreases with increasing amount of CaO (~6wt%) irrespective of Fe/SiO₂ ratio (1.4~1.7). However, the addition of alumina in the slag with Fe/SiO₂=1.5 linearly decreases the L_{Pb} , whereas there is a minimum value at about 4wt% Al₂O₃ at Fe/SiO₂=1.3.
- 2) The log L_{Pb} continuously decreases with increasing Fe/SiO₂ ratio and furthermore, the addition of Al₂O₃ (5~15wt%) into the silica saturated iron silicate slag (Fe/SiO₂ < 1.0) shows the highest Pb distribution ratio. This is mainly due to a decrease in the activity of FeO even at silica saturation condition.
- 3) The log L_{Pb} and log (Fe³⁺/Fe²⁺) shows a linear relationship with the slope of about -0.44, which was slightly lower than the expected value of -2/3. This probably originates from the attraction between Pb²⁺ and ferric complex ions with increasing Fe³⁺/Fe²⁺ ratio.
- 4) The Pb distribution ratio increases with increasing content of Cu₂O in the slag and the excess free energy of PbO decreases with increasing content of Cu₂O, indicating that Cu₂O is relatively more acidic than PbO in the copper smelting iron silicate slags. However, in viewpoint of copper loss into the slag, the silica saturated system containing small amounts of alumina is strongly recommended to stabilize PbO in slag phase at low content of Cu₂O.

References

- [1] M. Nagamori, P.J. Mackey and P. Tarassoff. Copper Solubility in FeO-Fe₂O₃-SiO₂-Al₂O₃ Slag and Distribution Equilibria of Pb, Bi, Sb and As between Slag and Metallic Copper. *Metall. Trans. B.*, 1975, 6B, p295-301.
- [2] A.K. Kylo and G.G. Richards. Kinetic Modeling of Minor Element Behavior on copper converting. *Metall. Mater. Trans. B.*, 1998, 29B, p261-68.
- [3] H.G. Kim and H.Y. Sohn. Effects of CaO, Al₂O₃, and MgO Additions on the Copper Solubility, Ferric/Ferrous Ratio, and Minor-Element Behavior of Iron-Silicate Slags. *Metall. Mater. Trans. B.*, 1998, 29B, p583-90.
- [4] K. Matsuzaki, T. Ishikawa, T. Tsukada and K. Ito. Distribution Equilibria of Pb and Cu between CaO-SiO₂-Al₂O₃ Melts and Liquid Copper. *Metall. Mater. Trans. B.*, 2000, 31B, p1261-66.
- [5] M. Kudo, E. Jak, P. Hayes, K. Yamaguchi and Y. Takeda. Lead Solubility in FeO_x-CaO-SiO₂ Slags at Iron Saturation. *Metall. Mater. Trans. B.*, 2000, 31B, p15-24.
- [6] S.A. Decterov and A.D. Pelton. Thermodynamic modeling of Lead distribution among Matte, Slag, and Liquid Copper. *Metall. Mater. Trans. B.*, 1999, 30B, p1033-44.
- [7] M. Kashima, M. Eguchi and A. Yazawa. Distribution of impurities between Crude Copper, White Metal and Silica-Saturated Slag. *Trans. JIM*, 1978, 19, p152-58.
- [8] C. Acuna and A. Yazawa. Behaviours of Arsenic, Antimony and Lead in Phase Equilibria among Copper, Matte and Calcium or Barium Ferrite Slag. *Trans. JIM*, 1987, 28, p498-506.
- [9] E.T. Turkdogan. *Physical Chemistry of High Temperature Technology*, Academic Press, New York, NY, 1980, p1-24.
- [10] N. Sano. Thermodynamics of Slags (Chapter 2), in *Advanced Physical Chemistry for Process Metallurgy*, ed. by N. Sano, W.K. Lu, P.V. Riboud and M. Maeda, Academic Press, San Diego, CA, 1997, p46-51.

- [11] C.W. Bale, E. Belisle, P. Chartrand, S.A. Deckerov, G. Eriksson, K. Hack, I.-H. Jung, Y.-B. Kang, J. Melancon, A.D. Pelton, C. Robelin and S. Petersen: *Calphad*, 2009, 33, p295-311.
- [12] M.O. Suk and J.H. Park. Corrosion Behaviors of Zirconia Refractory by CaO-SiO₂-MgO-CaF₂ Slag. *J. Am. Ceram. Soc.*, 2009, 92, p717-23.
- [13] H. Larson and J. Chipman. Oxygen Activity in Iron oxide Slags. *J. Met.*, 1953, 5, p1089-96.
- [14] M. Nevriiva and K. Fischer. Contribution to the binary phase diagram of the system PbO-Fe₂O₃. *Mater Res. Bull.*, 1986, 21, p1285-90.
- [15] A.J. Mountvala and S.F. Ravitz. Phase Relations and Structures in the System PbO-Fe₂O₃. *J. Am. Ceram. Soc.*, 1962, 45, p285-88.
- [16] K. Yamaguchi, S. Ueda and Y. Takeda. Phase equilibrium and thermodynamic properties of CaO-SiO₂-FeO_x slags for Copper smelting- research achievements of Professor Yoichi Takeda. *Scand. J. Metall.*, 2005, 34, p164-74.
- [17] R.U. Pagador, M. Hino and K. Itagaki. Solubility of Ni, Cu and Minor Elements in FeO_x-SiO₂-MgO Slag Equilibrating with Nickel Alloy. *Proc. 5th Int. Conf. on Molten Slags, Fluxes and Salts '97*, Sydney, Jan. 5-8, 1997, ISS, Warrendale, PA, p321-27.
- [18] N. Moon, M. Hino, Y. Lee and K. Itagaki. PbO activity and Impurity Dissolution in PbO-FeO_x-CaO-SiO₂ Slag. *Proc. 5th Int. Conf. on Molten Slags, Fluxes and Salts '97*, Sydney, Jan. 5-8, 1997, ISS, Warrendale, PA, p753-59.
- [19] R.P. Das and G.W. Healy. Lead and Nickel Distribution in the Cu₂O-PbO-SiO₂ and the Cu₂O-NiO-SiO₂ Systems Equilibrated with Liquid Copper. *Metall. Trans. B.*, 1976, 7B, p529-36.
- [20] G.K. Sigworth and J.F. Elliot. The thermodynamics of dilute liquid copper alloys. *Can. Metall. Q.*, 1974, 13, p455-61.
- [21] S. Ban-ya. Mathematical Expression of Slag-Metal Reactions in Steelmaking Process by Quadratic Formalism Based on the Regular Solution Model. *ISIJ Int.*, 1993, 33, p2-11.